

R. ZACHARIASZ\*, D. BOCHENEK\*, K. DZIADOSZ\*, J. DUDEK\*, J. ILCZUK\*

## INFLUENCE OF THE Nb AND Ba DOPANDS ON THE PROPERTIES OF THE PZT TYPE CERAMICS

### WPLYW DOMIESZEK Nb i Ba NA WŁAŚCIWOŚCI CERAMIKI TYPU PZT

Investigations of an influence of an admixture of ions  $Ba^{2+}$  and  $Nb^{5+}$  on dielectric and piezoelectric properties of the  $Pb(Zr_{0.53}Ti_{0.47})O_3$  (PZT) ceramics were conducted. The PZT type ceramics was synthesized by a conventional method, and compacted by a free sintering method. The PZT type specimens were poling by a low and high temperature method. It was found that there was a positive influence of adding 10mol%Ba and ~2mol%Nb simultaneously on a set of dielectric and piezoelectric parameters, which are important for practical applications of this PZT type ceramics.

*Keywords:* poling, piezoelectric and dielectric properties, PZT type ceramics

W pracy przeprowadzono badania wpływu domieszki baru  $Ba^{2+}$  i niobu  $Nb^{5+}$  na dielektryczne i piezoelektryczne właściwości ceramiki  $Pb(Zr_{0.53}Ti_{0.47})O_3$  (PZT). Ceramika typu PZT była syntetyzowana metodą konwencjonalną, a zagęszczana metodą swobodnego spiekania. Próbki typu PZT polaryzowano metodą niskotemperaturową i wysokotemperaturową. Wykazano, że domieszkowanie ceramiki PZT domieszką Ba w ilości 10mol%Ba oraz domieszka niobu w ilości ok. 2mol% Nb wpływa pozytywnie na jej dielektryczne i piezoelektryczne właściwości, co jest niezwykle istotne dla jej praktycznych zastosowań.

### 1. Introduction

The PZT type ceramics constitutes a numerous family of binary ternary quaternary and pentnary solid solutions of which the  $(1-x)PbZrO_3-(x)PbTiO_3$  binary solid solution is the base. Wide isomorphism of this solution enables to substitute appropriate cations in the place of Pb, Zr and Ti [1-2]. An appropriate selection of the composition and conditions of a manufacturing technology allows obtaining the ceramics, which can be used widely in different types of piezoelectric transducers.

PZT of the  $Pb(Zr_{0.53}Ti_{0.47})O_3$  composition in the phase near the morphotropy boundary (OM) in the phase diagram (Fig.1a) constitutes the base for that type of materials [3-4]. This composition is diphas structuraly (the tetragonal phase ( $P4mm$ ) and the rhombohedral phase ( $R3m$ )). With an increase in the  $PbTiO_3$  concentration the structural phase transition  $R3m$  in  $P4mm$  (morphotropic phase transition) takes place in this solid solution. In PZT from this area in the phase diagram the domain structure is susceptible to an influence of an electric field what facilitates a poling process of the

ceramics. The PZT ceramics polarized shows the maximum values of piezoelectric parameters [5]. The first phase diagram of the  $(Pb_xBa_{1-x})(Zr_yTi_{1-y})O_3$  solid solution (Fig.1b) was proposed in 1959 by Ikeda [6], however in 1994 modified form of the diagram was presented [7].

The wide isomorphism of the PZT-based perovskite like ceramic materials enables to introduce dopants of the different valence into both positions A and positions B of the compound. PZT doping provides an opportunity to control electro-physical parameters of the ceramics and owing to it we can obtain materials of increased or decreased ferroelectric-hardness [8-9].

Ferroelectric and piezoelectric parameters of PZT type ceramics disappear at the Curie temperature, whereas depolarization processes commence at lower temperature ( $T_{dep} < T_C$ ). The chemical composition (the Zr/Ti concentration ratio and admixtures), a technological process to produce the ceramics and a way of the poling process have an influence on stability of a poling state, thus on stability of equipment operating parameters, using the ceramics [5].

\* UNIVERSITY OF SILESIA, DEPARTMENT OF MATERIALS SCIENCE, 41-200 SOSNOWIEC, 2 ŚNIEŻNA STR., POLAND

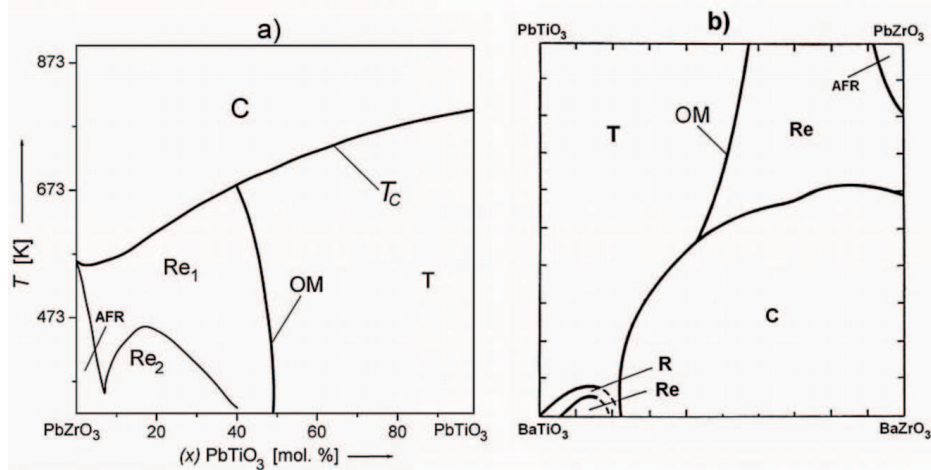


Fig. 1. A phase diagrams of the  $\text{PbTiO}_3 - \text{PbZrO}_3$  [3] (a) and  $\text{PbTiO}_3 - \text{PbZrO}_3 - \text{BaTiO}_3 - \text{BaZrO}_3$  [6] (b) solid solution at room temperature; where: T - tetragonal ferroelectric phase, R - rhombic ferroelectric phase, Re - rhombohedral ferroelectric phase, AFR - rhombic antiferroelectric phase, C - regular paraelectric phase

An aim of this work was to investigate an influence of admixtures of ions  $\text{Ba}^{2+}$  and ions  $\text{Nb}^{5+}$  introduced into the  $\text{Pb}(\text{Zr}_{0.53}\text{Ti}_{0.47})\text{O}_3$  solid solution on values of dielectric parameters, enabling to use this ceramics in acoustic engineering.

## 2. Experiment

In the work four compositions of the PZT type ceramic specimens were obtained: (I)  $\text{Pb}(\text{Zr}_{0.53}\text{Ti}_{0.47})\text{O}_3$  (PZT), (II)  $(\text{Pb}_{0.9}\text{Ba}_{0.1})(\text{Zr}_{0.53}\text{Ti}_{0.47})\text{O}_3$  (PBZT), (III)  $\text{Pb}(\text{Zr}_{0.53}\text{Ti}_{0.47})_{0.98}\text{Nb}_{0.02}\text{O}_3$  (PZTN) and (IV)  $(\text{Pb}_{0.9}\text{Ba}_{0.1})(\text{Zr}_{0.53}\text{Ti}_{0.47})_{0.98}\text{Nb}_{0.02}\text{O}_3$  (PBZTN). The initial components to obtain particular compositions of the PZT type were simple oxides:  $\text{PbO}$ ,  $\text{ZrO}_2$ ,  $\text{TiO}_2$ ,  $\text{Nb}_2\text{O}_5$  and the  $\text{BaCO}_3$  barium carbonate. The  $\text{PbO}$  lead oxide was added in excess. The powders underwent mixing, and then they were synthesized in the following conditions:  $T_{\text{pol}}=850^\circ\text{C}$  for  $t_{\text{synt.}}=2\text{h}$ . After the synthesis the powders were mixed once more, and next they were pressed into compacts and sintered by the free sintering method in the conditions:  $T_s=1200^\circ\text{C}/t_{s1}=3\text{h}$ .

For electric tests silver electrodes were spread on the polished surfaces of the ceramic specimens by a paste burning method.

The SEM microstructure and EDS examinations were made by a SEM scanning microscope with field emission, HITACHI S-4700, and with EDS Noran Vantage system, dielectric measurements were performed on a capacity bridge of a BR2817 type, with a heating rate of  $0.5^\circ/\text{min}$ , for a cycle of cooling at frequency of the measurement field  $\nu=1\text{kHz}$ . The PZT type specimens were poled by applying a dc electric field  $E_{\text{pol}}=40\text{kV}/\text{cm}$  for  $t_{\text{pol}}=40\text{min}$  at temperature  $T_{\text{pol}}=140^\circ\text{C}$  in the sil-

icon oil (the low temperature method), and in conditions  $E_{\text{pol}}=9\text{kV}/\text{cm}/t_{\text{pol}}=30\text{min}/T_{\text{pol}}=400^\circ\text{C}$  (the high temperature method) using a Matsusada Precision Inc. HEOPS-5B6 high voltage supply. Measurements of dielectric and piezoelectric parameters were conducted after 15 days from poling for the aging process to be completed. The piezoelectric parameters ( $k_p$ ,  $d_{31}$ ,  $Q_m$ ,  $S_{11}^E$ ,  $\nu_R$ ) were determined by a resonance/antiresonance method [10].

## 3. Results and discussion

The SEM micro-structural images of fractures of the PZT ceramic specimens are presented in Fig.2. The  $\text{Pb}(\text{Zr}_{0.53}\text{Ti}_{0.47})\text{O}_3$  non-doped ceramics has a strongly compacted microstructure, with the fracture through the grains, without clearly visible intergranular boundaries. Doping PZT with the barium and the niobium (PBZT, PZTN and PBZTN) improves the ceramic microstructure. The barium added to PZT increases the grain size (the fracture takes place mainly through the grain), while doping with the niobium decreases the average size of the ceramic grains (the fracture takes place mainly along the grain boundary). Simultaneous doping PZT with the barium and the niobium yields intermediate sizes of the ceramic grains (Fig.2d).

Composition homogeneity tests by the EDS point and surface method (Fig.3) confirmed the assumed qualitative and composition of the specimens made and presence of the initial components of the ceramic specimens. The EDS examination results are comparable to proportions of the initial components resulting from stoichiometry (the values in the brackets - Table 1).

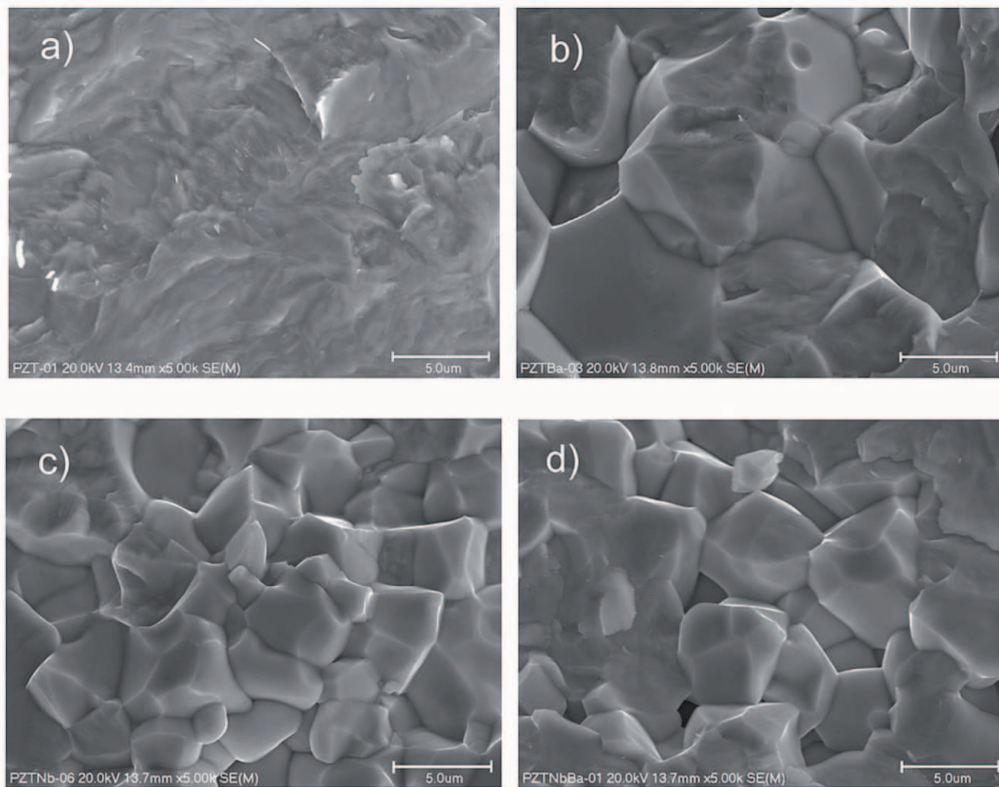


Fig. 2. An influence of dopants on the PZT type ceramics microstructure: a) PZT, b) PBZT, c) PZTN, d) PBZTN

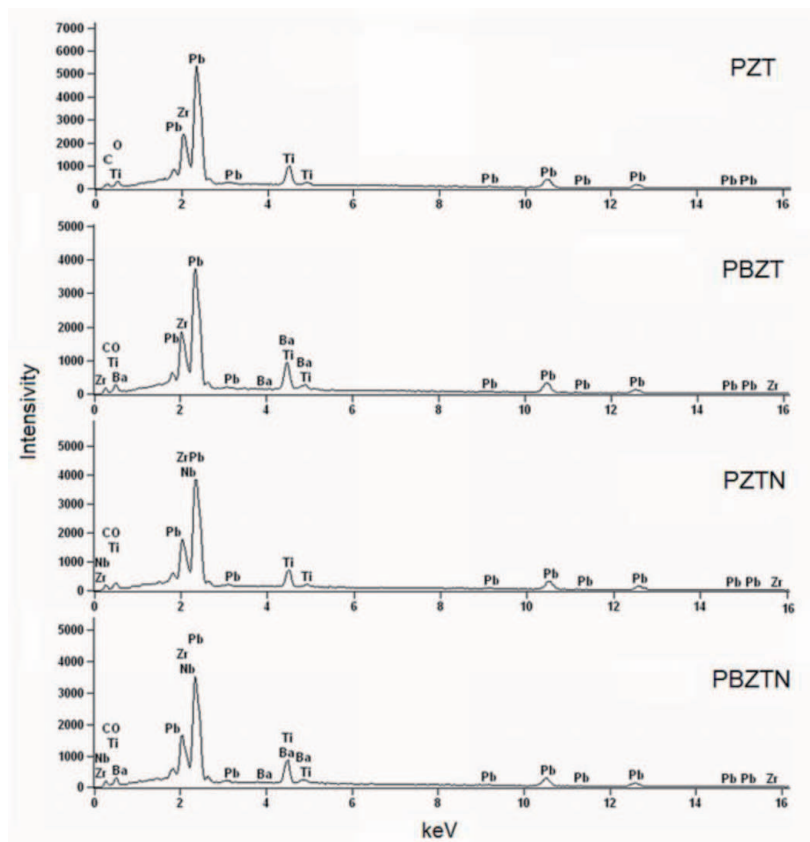


Fig. 3. EDS of the PZT type ceramics

Specification of the percentage amounts of the initial components of particular compounds of the PZT type obtained from the EDS examinations

	PZT	PBZT	PZTN	PBZTN
PbO [weight %]	68.32 (68.45)	62.48 (62.96)	67.90 (68.14)	62.17 (62.66)
BaO [weight %]	–	4.59 ( 4.81)	–	4.84 (4.78)
TiO <sub>2</sub> [weight %]	12.05 (11.52)	12.19 (11.76)	11.62 (10.90)	11.67 (11.15)
ZrO <sub>2</sub> [weight %]	19.63 (20.03)	20.74 (20.47)	18.51 (18.96)	19.32 (19.38)
Nb <sub>2</sub> O <sub>5</sub> [weight %]	–	–	1.97 (2.00)	2.00 (2.03)

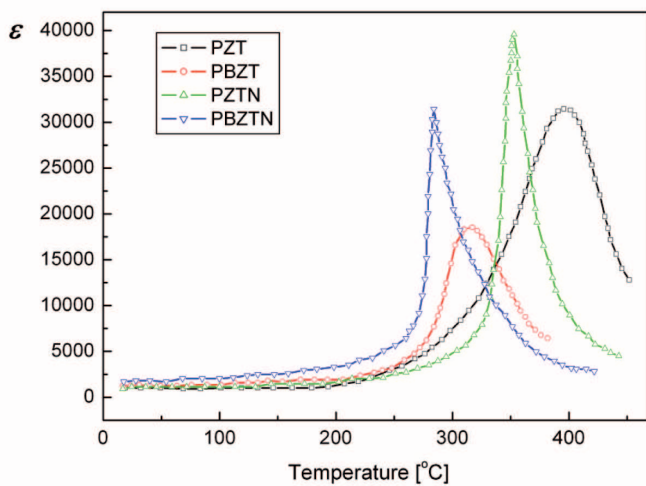


Fig. 4. Temperature relationships of electric permittivity for the PZT type ceramics (a heating cycle)

The characteristic behaviour of the  $\varepsilon(T)$  courses, typical for the ferroelectrics, is observed on the temperature relationships of electric permittivity of the PZT type ceramic compositions obtained. For the non-doped PZT and PBZT compositions the phase transition from the ferroelectric to paraelectric phase takes place in a wide range of temperatures (the diffused phase transition). The PZTN and PBZTN are characterized by a sharp phase transition. The non-doped PZT ceramics has the highest temperature of the phase transition, and adding the Ba and Nb dopants results in a considerable displacement of the Curie temperature towards lower temperatures (Table 2). The barium dopant added to PZT decreases the maximum value of electric permittivity ( $\varepsilon_m$ ) at  $T_m$ , whereas the niobium dopant gives an increase in  $\varepsilon_m$ . Simultaneous doping PZT with the niobium and barium dopant lowers the phase transition temperature, and the values of the electric permittivity are intermediate. As for the PZT composition doped with the niobium (PZTN), the ferroelectric phase transition in PBZTN has a sharp character. In the work [11], the analysis of influence the Nb and Sr admixture on the properties on the  $\text{Pb}(\text{Zr}_{0.53}\text{Ti}_{0.47})\text{O}_3$  ceramics was presented. This material

shows equally high values  $\varepsilon_m$  and high temperature of the phase transition  $T_m$ , in comparison with PZT ceramics with Nb and Ba admixture.

The temperature relationships of the tangent of the angle of dielectric losses  $\tan\delta(T)$  for the PZT type ceramics for the measurement field frequency  $\nu=1.0\text{kHz}$  are presented in Fig.5. The typical behaviour of the ferroelectrics in the  $\tan\delta(T)$  diagrams is presence of the characteristic maximum of the  $\tan\delta$  value just before the phase transition. It is clearly visible for the doped compositions of the PZT type ceramics. Doping PZT with the barium and the niobium lowers dielectric losses. The best effects to minimize the dielectric losses are given by simultaneous doping PZT with the niobium and the barium in the optimum amounts (Table 2).

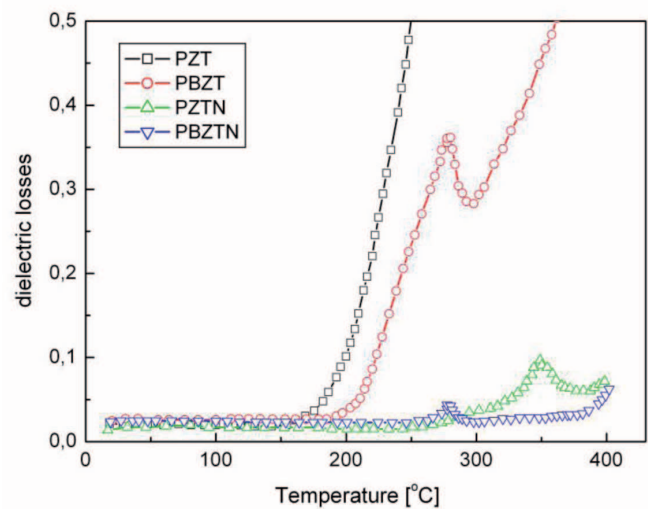


Fig. 5. Temperature relationships of the tangent of the dielectric loss angle for the PZT type ceramics (a heating cycle)

The 10mol%Ba<sup>2+</sup> dopant makes the PZT ceramics harder dielectrically (lower  $\varepsilon$  and  $\tan\delta$  values, a bigger coercion field  $E_C$  and greater mechanical quality factor and a slight increase in the piezoelectric parameter values). This ceramics is less susceptible to depolarization than the non-doped PZT ceramics, what increases stability of working parameters of such a piezo-element. The



barium ion ( $R_{Ba}=0.144\text{nm}$ ) occupies the lead position ( $R_{Pb}=0.126\text{nm}$ ) in PZT. As an iso-valence ion,  $\text{Ba}^{2+}$  does not make a change of through electric conductivity, but only slight changes of other parameters. The conducted tests showed that 10mol% dopants of the barium added to PZT are the optimum amount.

TABLE 2

Influence of  $\text{Ba}^{2+}$  and  $\text{Nb}^{5+}$  admixtures on values of the piezoelectric and dielectric parameters of the PZT type ceramics

Ceramics	PZT	PBZT	PZTN	PBZTN
$\rho \times 10^3 [\text{g/cm}^3]$	7.53	7.58	7.56	7.58
$T_m$ [°C]	397	316	351	285
$\varepsilon$ at $T_m$	31370	18420	39440	31370
$\tan\delta$ [%] at $T_r$	0.85	0.71	1.69	2.19
$\rho_v \times 10^{-12} [\Omega\text{m}]$	0.32	0.33	0.29	0.39
$\varepsilon_{33}^s/\varepsilon_0$ at $T_r$	1263	1180	1420	1380
$P_r$ [C/m <sup>2</sup> ]	0.27	0.25	0.30	0.50
$E_C$ [kV/cm]	1.40	1.48	1.20	1.32
$k_p$	0.41	0.35	0.50	0.58
$k_{31}$	0.31	0.30	0.29	0.28
$d_{31} \times 10^{-12}$ [C/N]	-68	-62	-132	-135
$d_{33} \times 10^{-12}$ [C/N]	~ 218	~ 213	~ 340	~ 380
$Q_m$	700	~ 800	~ 500	~ 185
$V_R$ [m/s]	2534	~ 2610	~ 2530	2820
$S_{11}^E \times 10^{12}$ [m <sup>2</sup> /N]	10.5	10.8	11.2	9.74

In case of the doped  $\text{Nb}^{5+}$  cations, because of a small ionic radius ( $R_{Nb}=0.069\text{nm}$ ), they can occupy a position of  $\text{Ti}^{4+}$  ( $R_{Ti}=0.068\text{nm}$ ) or  $\text{Zr}^{4+}$  ( $R_{Zr}=0.079\text{nm}$ ) in the base PZT. Substitution of ions of higher valence results in lead vacancy formation ( $V_{Pb}$ ) to neutralize a specimen electrically [12]. Since the electric conductivity of the pure PZT is a hole type ( $p$ -type), the surplus of electrons compensates holes and electric conductivity decreases ( $\rho_v$ - increases). As a result it lowers anchoring of the domains by free charges and it facilitates poling and re-poling process. The soft  $\text{Nb}^{5+}$  dopant causes the following changes of the PZT parameters: there is an increase in values of electric permittivity  $\varepsilon$ ,  $\tan\delta$ , electromechanical coupling  $k_p$ , a piezoelectric modulus  $d_{ij}$ , flexibility  $S_{ij}$ , resistivity  $\rho_v$  and internal friction  $Q_m^{-1}$ , whereas values of a coercion field  $E_C$  and a mechanical quality factor  $Q_m$  decrease (PZTN in table 2). 2.0 mol.%  $\text{Nb}^{5+}$  dopant is the optimum amount resulting in lowering hardness of the  $\text{Pb}(\text{Zr}_{0.53}\text{Ti}_{0.47})\text{O}_3$  ceramics. Analysis of influence of the Ba and Nb admixture on the proper-

ties of PBZT type ceramics has been presented widely in work [13].

#### 4. Conclusions

The  $\text{Pb}(\text{Zr}_{0.53}\text{Ti}_{0.47})\text{O}_3$  based ceramics was obtained in the work and it was doped with barium and niobium. It has been found that the optimum amount of the barium dopant in PZT, which makes it ferro-electrically hard, is 10.0mol%  $\text{Ba}^{2+}$ . In the case of doping PZT with niobium the optimum amount, which lowers ferroelectric hardness of the ceramics, is 2.0 mol.%  $\text{Nb}^{5+}$ .

Simultaneous doping PZT with the both  $\text{Ba}^{2+}$  and  $\text{Nb}^{5+}$  admixtures improves a set of the piezoelectric parameters of the ceramics. The PBZTN ceramics has the highest density and maintains high values of  $k_p$ ,  $d_{31}$  i  $d_{33}$  at slight changes of other parameters. This ceramics can be poling easily and it ages insignificantly. The polarized PBZTN ceramics shows high stability of resonance frequency  $\Delta f_r/f_r < 0.2\%$  in the temperature range (0÷85°C). Poling the PNZTN ceramics by the high temperature method yields better stability of its piezoelectric parameters comparing to the low temperature poling method (Fig.6).

The PZT type ceramics obtained meets the requirements for applications e.g. in bio-morphic piezoelectric transducers and medium power ignition transducers.

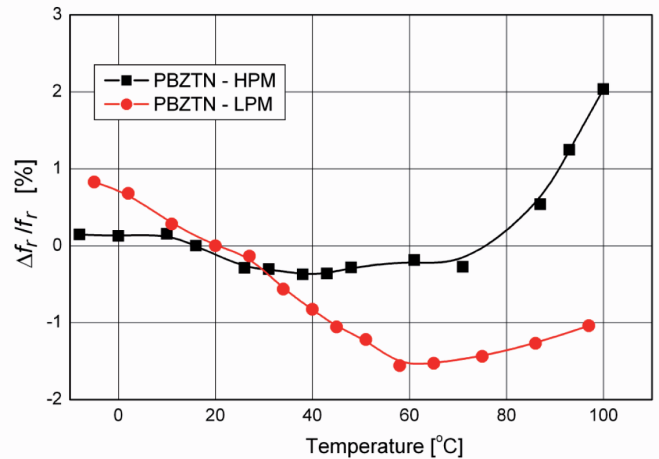


Fig. 6. An influence of the poling method on stability of the resonance frequency  $\Delta f_r/f_r$  of the PBZTN ceramics. HPM – poling by the high temperature method, LPM – poling by the low temperature method

#### Acknowledgements

Work supported by Polish Grant N R15 0005 04.

## REFERENCES

- [1] E.G. Fesenko, A.Ya. Danciger, O.N. Rozumovskaya, *Novye piezokeramicheskiye materialy*, Izd. RGU, Rostov na Donu, 49-70 (1983).
- [2] I. Franke, K. Roleder, L. Mitoseriu, R. Piticescu, Z. Ujma, High-temperature macroscopic piezoelectricity in Nb-doped  $\text{PbZr}_{1-x}\text{Ti}_x\text{O}_3$  ceramics driven by the existence of polar regions, *Phys. Rev. B* **73**, 144114-1-5 (2006).
- [3] B. Jaffe, W.R. Cook, H. Jaffe, *Piezoelectricheskaya keramika*, Izd. "Mir" Moskva, 139-147 (1974).
- [4] B. Noheda, J.A. Gonzalo, L.E. Cross, R. Guo, S.-E. Park, D.E. Cox, G. Shirane, Tetragonal-to-monoclinic phase transition in a ferroelectric perovskite: The structure of  $\text{PbZr}_{0.52}\text{Ti}_{0.48}\text{O}_3$ , *Phys. Rev. B* **61**, 8687-9695 (2000).
- [5] J. Dudek, D. Bochenek, M.F. Kupriyanov, Z. Surowiak, Wpływ składu chemicznego i warunków otrzymywania na stabilność parametrów piezoceramiki typu PZT, *Ceramics* **65**, 93-100 (2001).
- [6] T. Ikeda, Studies on (Ba-Pb)(Ti-Zr) $\text{O}_3$  System, *Journal of Physical Society of Japan*, **14**, 2 168-174 (1959).
- [7] G. Li, G. Haertling, Dielectric, ferroelectric and electric field-induced strain properties of  $(\text{Pb}_{1-x}\text{Ba}_x)(\text{Zr}_{1-y}\text{Ti}_y)\text{O}_3$  ceramics, *Ferroelectrics* **166**, 31 (1995).
- [8] Z. Surowiak, D. Bochenek, Modyfikowanie składu chemicznego elektroceramiki PZT, *Materiały ceramiczne/ Ceramic Materials/*, **4**, 124-134 (2004).
- [9] R. Zachariasz, D. Bochenek, Properties of the PZT type ceramics admixed with barium and niobium, *Archives of Metallurgy and Materials*, **54**, 895-902 (2009).
- [10] K. Okadzaki, *Technologia ceramicznych dielektryków*, Izd. "Energia", Moskva, 233-235 (1976).
- [11] I. Franke, K. Roleder, J. Klimontko, A. Ratuszna, A. Soszyński, Anomalous piezoelectric and elastic properties of a tetragonal PZT ceramic near morphotropic phase boundary, *J. Phys. D: Appl. Phys.* **38**, 749 (2005).
- [12] J. Dudek, D. Bochenek, Z. Surowiak, V.G. Gavrilychenko, Wpływ warunków technologicznych na stabilność właściwości piezoelektrycznych ceramiki typu PZT, *Ceramics*, **79**, 130-136 (2003).
- [13] M. Adamczyk, Z. Ujma, L. Szymczak, Effect of Nb doping on the relaxor behaviour of  $(\text{Pb}_{0.75}\text{Ba}_{0.25})(\text{Zr}_{0.70}\text{Ti}_{0.30})\text{O}_3$  ceramics, *Journal of the European Ceramic Society*, **26**, 331-336 (2006).