

M. IBRAHIM^{1,2}, W.M. WAN IBRAHIM^{2,3}, M.M. AL BAKRI ABDULLAH^{1,2},
A.S. SAUFFI^{1,2}, R. AHMAD^{2,3}

HYDROGEN PEROXIDE MODIFICATION ENHANCES THE ABILITY OF METAKAOLIN BASED ALKALI ACTIVATED MATERIALS ADSORBENT TO REMOVE THE Ni²⁺ IONS

The presence of nickel ions in wastewater is a significant environmental concern due to its toxicity, which can cause severe health problems. Metakaolin is a pozzolanic material that can be activated by alkali to produce a highly porous and reactive material that can be utilised as a heavy metal ion adsorbent. However, the adsorption capacity of metakaolin-based adsorbents is limited by their surface chemistry and porosity. Metakaolin-based alkali-activated materials adsorbent modified with hydrogen peroxide can effectively remove nickel ions from wastewater. The modification process increases the surface area and porosity of the adsorbent, enhancing its adsorption capacity. The modified adsorbent (1.00 wt.% H₂O₂) showed a higher sorption capacity of 26.57 mg/g and efficiency of 85.22% compared to the non-modified adsorbent (10.55 mg/g) sorption capacity and 45.63% nickel removal efficiency, indicating the potential of hydrogen peroxide-modified adsorbents as an economical and ecologically sustainable solution for environmental applications, particularly for metal immobilization.

Keywords: Metakaolin; Alkali activated materials; Adsorbent; Ni²⁺ removal; Heavy metals

1. Introduction

A significant and ongoing environmental issue is the occurrence of heavy metals in industrial wastewater because of their non-biodegradability and toxicity [1,2]. One of the most prevalent heavy metals in industrial wastewater is nickel, which harms people and plants. Nickel is widely used in various industrial operations, such as electroplating, paint, textile production, paper and battery manufacture. In addition, mining and metallurgical operations are also significant sources of nickel contamination due to their extensive utilization. Since this type of heavy metal is poisonous and carcinogenic, its removal from wastewater is thus of utmost significance [3,4]. For the removal of heavy metals, several techniques have been used, including chemical precipitation, membrane filtration, coagulation, ion exchange, and adsorption [5,6]. Adsorption is one of the approaches for removing heavy metals from water effluents among the many treatment procedures because of its ease of use, efficiency, and affordability [7-10]. The adsorbents employed for the adsorption of heavy metals might be of mineral origins, such as natural zeolite, calcium silicate powders, and natural clay [11-14]. Common adsorbents,

including activated carbon, alumina and silica, have high levels of efficiency, but their high manufacturing costs limit their use [15-17]. It is increasingly important to create eco-friendly and affordable technology to protect the environment and promote sustainability. As a result, efforts are being made to create affordable, alternative metakaolin-based alkali activated materials adsorbents.

Alternative low-CO₂ binders to Portland cement, such as alkali-activation (or geopolymer) technology, are a subset of this technology and have received a great deal of interest in the recent decade for their potential in water and wastewater treatment [18-21]. Many inorganic wastes may be converted into useful products using alkali-activation technology. This is essential for furthering the circular economy [22-24]. By treating aluminosilicate precursors with concentrated alkali hydroxide and silicate solutions at (near) ambient conditions, alkali-activated materials (AAMs) may be made using a comparatively easy and less energy-intensive preparation approach [18,25]. The negatively charged aluminosilicate framework that makes up the chemical structure of AAMs allows charge-balancing cations to exchange with cations in the solution, which raises the prospect of employing them as adsorbents [26,27]

¹ UNIVERSITI MALAYSIA PERLIS (UNIMAP), FACULTY OF CHEMICAL ENGINEERING & TECHNOLOGY, KOMPLEKS PUSAT PENGAJIAN JEJAWI 3, 02600, ARAU, PERLIS, MALAYSIA

² UNIVERSITI MALAYSIA PERLIS, CENTER OF EXCELLENCE GEOPOLYMER AND GREEN TECHNOLOGY (CEGEOGTECH), 01000, KANGAR, PERLIS, MALAYSIA

³ UNIVERSITI MALAYSIA PERLIS (UNIMAP), FACULTY OF MECHANICAL ENGINEERING & TECHNOLOGY, 02600, ARAU, PERLIS, MALAYSIA

* Corresponding author: wannastura@unimap.edu.my



Adding hydrogen peroxide, which is well known to break down quickly in alkaline solution, is one of the preliminary requirements for synthesizing alkali activated materials adsorbents [28,29]. The AAMs structure might capture the oxygen produced, enhancing the material's porosity characteristics and, therefore, its adsorption performance while maintaining its surface chemistry [30-33]. The final products often feature a porous structure, great physical and chemical stability, an amorphous structure, and ion exchange capacities [34-36]. Some of the precursors are industrial waste products or other easily accessible, low-cost resources, which further improve the practicality from an economic and environmental standpoint.

The role of hydrogen peroxide in declaring alkali-activated materials better at absorbing or worse at absorbing cannot be measured or inferred. In particular, for alkali activated materials based on pozzolan, it has not yet been described how hydrogen peroxide affects the textural and adsorption properties of these materials. This research aimed to develop a hydrogen peroxide-modified pozzolan-based alkali activated material as an eco-adsorbent to improve the adsorption properties of metakaolin-based alkali activated materials. The impacts of hydrogen peroxide incorporation on the textural, structural, and adsorptive performance for nickel ion removal from aqueous solution were investigated and reported herein.

2. Experimental method

2.1. Materials

In this study, kaolin from Kaolin Sdn. Bhd. Tapah, Perak, Malaysia, served as aluminosilicate materials that were first calcined to create metakaolin. Metakaolin was used in this experiment, which was confirmed by X-ray fluorescence (XRF) elemental analysis, with the main silica oxide (SiO_2) content of 56.84% and aluminium oxide (Al_2O_3) composition of 35.60%. Technical-grade sodium hydroxide (NaOH) and sodium silicate solution (Na_2SiO_3) were utilized as an alkaline activator. Hydrogen peroxide, H_2O_2 , and Tween 80 surfactant were introduced as colourless foaming agents. Nickel ions stock was dissolved with the required weight of $\text{Ni}(\text{NO}_3)_2 \cdot 6\text{H}_2\text{O}$ in distilled water to create solutions containing nickel ions.

2.2. Geopolymer synthesis and analysis

The metakaolin as resource material was mixed with 8M sodium hydroxide solution and sodium silicate solution to create paste specimens at metakaolin/alkaline activator ratio 0.8 by mass of solid. The mass ratio of $\text{Na}_2\text{SiO}_3/\text{NaOH}$ was kept constant at 0.5 in this experiment. With a constant of 3 wt.% of Tween 80, the hydrogen peroxide, H_2O_2 , was changed from 0.50 wt.%, 0.75 wt.%, and 1.00 wt.% by mass of metakaolin. For comparison, a control sample was made without using a foaming agent. Alkali activated materials paste began to take

shape after adding all the ingredients. The resultant slurry was then shaped into the appropriate shape, which measured around 1 cm (formed into a small round shape). The sample was put in a steel tray hermetically sealed to prevent moisture from evaporating and placed in an oven to cure at 60°C for 24 hours. The samples of metakaolin-based alkali-activated materials were taken out of the oven after 24 hours and left to rest for 7 days before testing. The alkali-activated materials were processed into a powder form suitable for sorption operations by crushing and sieving through a $150\ \mu\text{m}$ particle size sieve. The resulting powder was washed with acetone at least three times to eliminate any excess alkaline activator solution. Using the Micrometrics Tristar II 3020 volumetric adsorption/desorption device, the Brunauer, Emmet, and Teller (BET) techniques were used to calculate the specific surface area and pore volume. SEM was used to characterize the structural characteristics of a sample of metakaolin alkali activated materials with varying hydrogen peroxide contents (SEM).

2.3. Adsorption test

For the adsorption test, 0.1 L of metal solution and 0.15 g of adsorbent were agitated to study the sorption of nickel ions on metakaolin-based alkali activated materials. The adsorption test was carried out at room temperature with the initial concentration of 100 mg/L fixed at pH 7. The pH values of the metal ion solutions were fixed by adjusting them with negligible quantities of 0.01M HCl and 0.01M NaOH. The orbital shaker was used with the flasks for 50 minutes at 150 rpm. Atomic absorption spectroscopy, or AAS, was used to analyze samples for the presence of Ni^{2+} and to determine the concentration of nickel ions in the filtered sample. The experiment was carried out three times for each condition to get the mean results. Eqs. (1) and (2) were used to determine the nickel removal efficiency, R , and the quantity of nickel adsorption on the metakaolin-based alkali activated materials sample, q_e .

$$q_e = \frac{(C_0 - C_e)V}{m} \quad (1)$$

$$R = \frac{(C_0 - C_e)}{C_0} \times 100\% \quad (2)$$

Where C_0 and C_e are the initial and equilibrium concentrations (mg/L), respectively, of nickel ions in solution, V is the volume (L) and m is the mass (g) of the adsorbent.

3. Results and discussions

3.1. Surface area and total pore volume analysis

TABLE 1 shows the BET surface areas and pore volumes of metakaolin-based AAMs adsorbents at various hydrogen peroxide concentrations determined from Nitrogen, N_2 adsorption.

Unfoamed metakaolin-based alkali activated materials have the lowest surface area and pore volume, measuring $7.1216 \text{ m}^2/\text{g}$ and $0.028246 \text{ cm}^3/\text{g}$, respectively. The surface area and pore volume of the hydrogen peroxide added to metakaolin-based alkali activated materials are larger than those of the control sample, maximum of 1.0 wt.% H_2O_2 concentration with $28.6057 \text{ m}^2/\text{g}$ of surface area and $0.194348 \text{ cm}^3/\text{g}$ of the pore volume. According to Mondal et al., 2021 [37] and Suresh Kumar et al., 2019 [38], increasing pore volume and surface area increased the number of active sorption sites. Thus, more active functional groups are exposed, which may increase the ability of nickel ions to bind to surfaces and remove them more effectively.

TABLE 1

Textural properties of metakaolin based alkali activated materials adsorbent

Samples	Specific Surface Area, S_{BET} (m^2/g)	Pore Volume, V (cm^3/g)
Control sample	7.1216	0.028246
0.50 wt.%	10.8483	0.100423
0.75 wt.%	24.6076	0.171588
1.00 wt.%	28.6057	0.194348

3.2. Microstructural analysis

Using a scanning electron microscope, (SEM) the surface of the inner sample structure was examined. AAMs samples of the control sample, 0.5 wt.%, and 1.0 wt.% hydrogen peroxide contents were chosen for analysis and study.

The quantity of hydrogen peroxide impacts the microstructure of geopolymers made from metakaolin (Fig. 1). Surfactant is added to the fixed volume as a stabilizing agent, which helps govern the pore-dispersion of metakaolin-based alkali activated materials [39]. The surfactant also stopped pore coalescence from becoming too extreme. This is shown by the little variations in the average pore diameter (Fig 1). The metakaolin-based AAMs control sample had the densest AAMs matrix since it lacked

a foaming component. Adding hydrogen peroxide to samples of AAMs may modify the reaction kinetics and microstructure of the material [40]. This can occur when hydrogen peroxide breaks into water and oxygen gas, creating porosity in the AAMs sample. Thus, hydrogen peroxide can enhance the sample's surface area and porosity, boosting its ability to adsorb or remove heavy metals such as nickel ions.

The metakaolin-based AAMs displayed a loose and porous structure that diffused evenly throughout the matrix by adding hydrogen peroxide. The addition of H_2O_2 increased pore volume and average pore size. Hajimohammadi et al., 2017 [41] and Korat & Ducman, 2017 [42] supported the idea that the geometric form of pores changes when H_2O_2 concentration rises. All small diameter pores were spherical and homogeneous in structure at low H_2O_2 (0.5 wt.%). High H_2O_2 concentrations up to 1.00 wt.% enhanced the likelihood of larger holes forming. Pore walls in these samples were very thin due to the substantial amount of foaming, which allowed certain pores to merge and create these enormous voids.

3.3. Adsorption capacity and removal efficiency analysis

Figs. 2 and 3 depict the adsorption capacity and the nickel ions removal efficiency from the outcomes of an adsorption test using foaming agents in various concentrations on samples of metakaolin-based alkali activated materials, respectively. The pattern demonstrated that the metakaolin-based AAMs samples adsorption capacity and removal effectiveness increase linearly with an increase in hydrogen peroxide concentration.

At 1.0 wt.% addition of hydrogen peroxide, the maximum removal efficiency of 85.22% was attained, leading to the adsorption of $26.57 \text{ mg}/\text{g}$ of nickel ions. By contrast, nickel uptake and elimination efficiency were the lowest in the control sample (at $20.55 \text{ mg}/\text{g}$ and 65.92%, respectively) due to the lack of a porous structure. Increasing the concentration of hydrogen peroxide led to higher Ni^{2+} adsorption and removal efficiency,

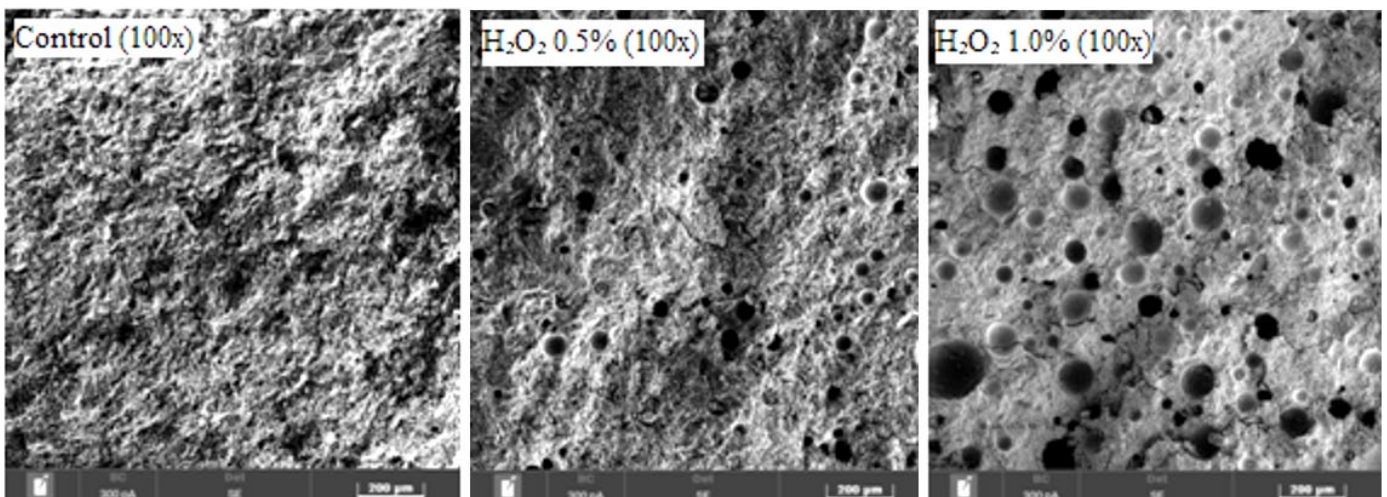


Fig. 1. SEM micrograph of metakaolin based alkali activated materials with different hydrogen peroxide content

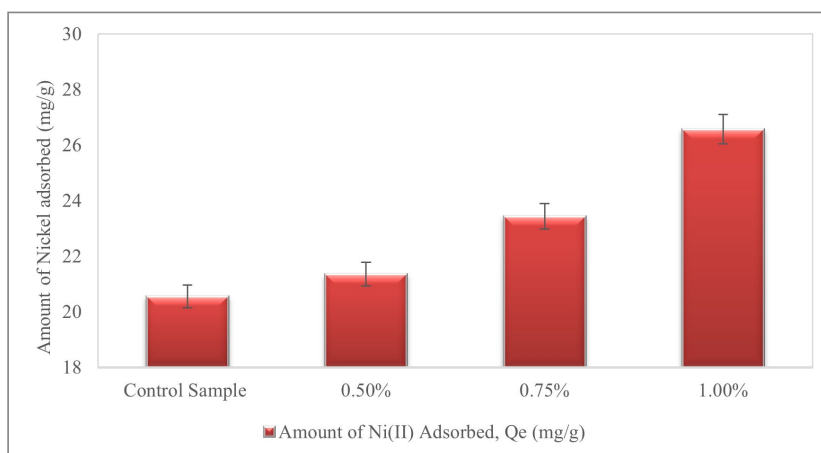


Fig. 2. Effect on hydrogen peroxide content on Ni(II) Adsorption quantity

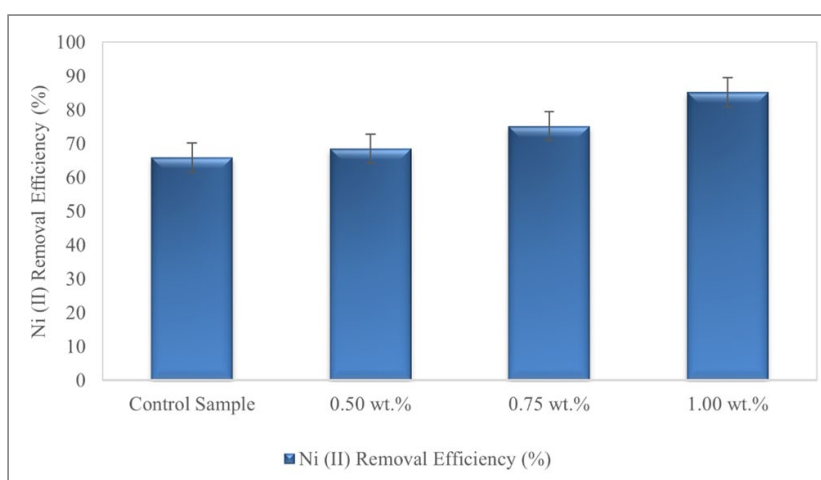


Fig. 3. Effect on hydrogen peroxide content on Ni(II) Removal Efficiency

suggesting that the alkali-activated materials' adsorption capacity was improved by adding hydrogen peroxide. Adsorbent materials with a greater number of pores or higher porosity offer a larger surface area for the adsorption of heavy metal ions, resulting in increased adsorption capacity due to more active adsorption sites [43,44]. However, excessive use of foaming agents (>1.0 wt.%) can create too large, uneven, or irregular pores, which can impair mechanical strength and reduce its durability. This is because the viscosity of the mixture rises when the foaming agent is added, resulting in fewer bubbles bursting, which does not encourage the pore growth of alkali-activated materials that function as adsorbents [45-47].

4. Conclusions

The study investigated the effect of hydrogen peroxide modification on removing nickel ions using metakaolin-based alkali-activated materials as adsorbents. The results showed that adding hydrogen peroxide enhanced the adsorption capacity and efficiency of the adsorbent, leading to improved nickel ion removal. At a temperature of 60°C, which is lower than the

sintering temperature of typical zeolite or membranes used for heavy metals removal, the metakaolin-based AAMs adsorbent was created utilizing a simple method. The metakaolin-based AAMs adsorbent has a highly developed porous structure and larger surface area, facilitating nickel ion adsorption. Adding H₂O₂ is anticipated to enhance the efficiency of metakaolin-based AAMs adsorbent in removing nickel ions, as the control sample's surface chemistry and porosity may limit its effectiveness. The best conditions for Ni²⁺ elimination (85.22%) and adsorption capacity values of 26.57 mg/g were achieved with 1.0 wt.% hydrogen peroxide added at pH 7, 25°C adsorption condition, and a 50-minute contacting period. The study concluded that modifying metakaolin-based alkali-activated materials adsorbent with hydrogen peroxide can enhance its ability to remove nickel ions.

Acknowledgments

The author would like to acknowledge the Fundamental Research Grant Scheme (FRGS) support under grant number FRGS/1/2019/TK10/Uni-MAP/02/21 from the Ministry of Education Malaysia.

REFERENCES

- [1] D.G. della Rocca, R.M. Peralta, R. A. Peralta, E. Rodríguez-Castellón, R. de Fatima Peralta Muniz Moreira, Adding value to aluminosilicate solid wastes to produce adsorbents, catalysts and filtration membranes for water and wastewater treatment. *Journal of Materials Science* **56**, 2, 1039-1063 (2021).
- [2] S.S. Obaid, D.K. Gaikwad, M.I. Sayyed, K. Al-rashdi, P.P. Pawar, Heavy metal ions removal from waste water by the natural zeolites. *Materials Today: Proceedings* **5**, 9, 17930-17934 (2018).
- [3] İ. Kara, D. Yilmazer, S.T. Akar, Metakaolin based geopolymer as an effective adsorbent for adsorption of zinc(II) and nickel(II) ions from aqueous solutions. *Applied Clay Science* **139**, 54-63 (2017).
- [4] H. Jin, Y. Zhang, Q. Wang, Q. Chang, C. Li, Rapid removal of methylene blue and nickel ions and adsorption/desorption mechanism based on geopolymer adsorbent. *Colloids and Interface Science Communications* **45** (2021).
- [5] M.S. Al-Harashsheh, K. al Zboon, L. Al-Makhadmeh, M. Hararah, M. Mahasneh, Fly ash based geopolymer for heavy metal removal: A case study on copper removal. *Journal of Environmental Chemical Engineering* **3**, 3, 1669-1677 (2015).
- [6] T.H. Tan, K.H. Mo, T.C. Ling, S.H. Lai, Current development of geopolymer as alternative adsorbent for heavy metal removal. *Environmental Technology and Innovation* **18**, 100684 (2020).
- [7] S.A. Rasaki, Z. Bingxue, R. Guarecuco, T. Thomas, Y. Minghui, Geopolymer for use in heavy metals adsorption, and advanced oxidative processes: A critical review. *Journal of Cleaner Production* **213**, 42-58 (2019).
- [8] T.W. Cheng, M.L. Lee, M.S. Ko, T.H. Ueng, S.F. Yang, The heavy metal adsorption characteristics on metakaolin-based geopolymer. *Applied Clay Science* **56**, 90-96 (2012).
- [9] E. Da'na, Adsorption of heavy metals on functionalised-mesoporous silica: A review. *Microporous and Mesoporous Materials* **247**, 145-57 (2017).
- [10] N. Ariffin et al., Review on Adsorption of Heavy Metal in Wastewater by Using Geopolymer. *MATEC Web of Conferences* **97**, 01023 (2017).
- [11] H. Es-Sahbany et al., Removal of heavy metals (nickel) contained in wastewater-models by the adsorption technique on natural clay. *Materials Today: Proceedings* **13**, 866-875 (2019).
- [12] A. Esmaeili, M. Mobini, H. Eslami, Removal of heavy metals from acid mine drainage by native natural clay minerals, batch and continuous studies. *Applied Water Science* **9**, 4, 1-6 (2019).
- [13] S. Andrejkovičová et al., The effect of natural zeolite on microstructure, mechanical and heavy metals adsorption properties of metakaolin based geopolymers. *Applied Clay Science* **126**, 141-152 (2016).
- [14] M. Ridhwan et al., The adsorptive removal of chromium (VI) in aqueous solution by novel natural zeolite based hollow fibre ceramic membrane. *Journal of Environmental Management* **224**, 252-262 (2018).
- [15] H. Niu et al., Recycling mica and carbonate-rich mine tailings in alkali-activated composites: A synergy with metakaolin. *Minerals Engineering* **157**, 106535 (2020).
- [16] N. Ariffin, M. Mustafa, A. Bakri, R. Rozainy, Geopolymer as an Adsorbent of Heavy Metal: A Review. *AIP Conference Proceedings* **020030** (2017).
- [17] S.N.A. Abas, M.H.S. Ismail, M.L. Kamal, S. Izhar, Adsorption process of heavy metals by low-cost adsorbent: A review. *Research Journal of Chemistry and Environment* **18**, 4, 91-102 (2013).
- [18] J.L. Provis, Cement and Concrete Research Alkali-activated materials. *Cement and Concrete Research* **114**, 40-48 (2018).
- [19] T. Luukkonen, Z. Abdollahnejad, J. Yliniemi, P. Kinnunen, M. Ilkainen, One-part alkali-activated materials: A review. *Cement and Concrete Research* **103**, July 2017, 21-34 (2018).
- [20] B.C. Mendes et al., Application of eco-friendly alternative activators in alkali-activated materials: A review. *Journal of Building Engineering* **35**, August 2020 (2021).
- [21] T. Luukkonen, A. Heponiemi, H. Runtti, J. Pesonen, J. Yliniemi, U. Lassi, Application of alkali-activated materials for water and wastewater treatment: a review. *Reviews in Environmental Science and Biotechnology* **18**, 2, 271-297 (2019).
- [22] R.A. Razak, M. Mustafa, A. Bakri, K. Hussin, Optimisation of NaOH Molarity, LUSI Mud / Alkaline Activator, and Na₂SiO₃ / NaOH Ratio to Produce Lightweight Aggregate-Based Geopolymer. *International Journal of Molecular Sciences* **16**, 11629-11647 (2015).
- [23] A. Mehta, R. Siddique, An overview of geopolymers derived from industrial by-products. *Construction and Building Materials* **127**, 183-198 (2016).
- [24] R. Mohamed et al., Heat evolution of alkali-activated materials: A review on influence factors. *Construction and Building Materials* **314**, October 2021 (2022).
- [25] M. Ibrahim, W. Mastura Wan Ibrahim, M. Mustafa Al Bakri Abdullah, A. Syauqi Sauffi, A Review of Geopolymer Based Metakaolin Membrane as an Effective Adsorbent for Waste Water Treatment. *IOP Conference Series: Materials Science and Engineering* **864**, 1 (2020).
- [26] A. Martin, J.Y. Pastor, A. Palomo, A. Fernández Jiménez, Mechanical behaviour at high temperature of alkali-activated aluminosilicates (geopolymers). *Construction and Building Materials* **93**, 1188-1196 (2015).
- [27] A. Aizat, M.M.A. Abdullah, Y.M. Liew, C.Y.H.E., Dolomite / fly ash alkali activated geopolymer strengths with the influence of solid / liquid ratio Dolomite / Fly Ash Alkali Activated Geopolymer Strengths with the Influence of Solid / Liquid Ratio. *AIP Conference Proceedings* **2030**, 020274, November (2018).
- [28] W.M.W. Ibrahim, K. Hussin, M.M.A.B. Abdullah, A.A. Kadir, Geopolymer lightweight bricks manufactured from fly ash and foaming agent. *AIP Conference Proceedings* **1835**, (2017).
- [29] M.M. al Bakri Abdullah, K. Hussin, M. Bnhussain, K.N. Ismail, Z. Yahya, R.A. Razak, Fly ash-based geopolymer lightweight concrete using foaming agent. *International Journal of Molecular Sciences* **13**, 6, 7186-7198 (2012).
- [30] Z. Ji, L. Su, Y. Pei, Characterisation and adsorption performance of waste-based porous open-cell geopolymer with one-pot preparation. *Ceramics International* **47**, 9, 12153-12162 (2021).
- [31] S. Petlitckaia, A. Poulesquen, Design of lightweight metakaolin based geopolymer foamed with hydrogen peroxide. *Ceramics International* **45**, 1, 1322-1330 (2019).

- [32] A. Naveed, F. Saeed, M. Khraisheh, M. al Bakri, Noor-Ul-Amin, S. Gul, Porosity control of self-supported geopolymeric membrane through hydrogen peroxide and starch additives. *Desalination and Water Treatment* **152**, January, 11-15 (2019).
- [33] D.T. Hermann et al., Enhanced Performance of Hydrogen Peroxide Modified Pozzolan-Based Geopolymer for Abatement of Methylene Blue from Aqueous Medium. *Silicon* **14**, 5191-5206 (2022).
- [34] Q. Tang, Y. Yuan Ge, K. Tuo Wang, Y. He, X. Min Cui, Preparation and characterisation of porous metakaolin-based inorganic polymer spheres as an adsorbent. *Materials and Design* **88**, 1244-1249 (2015).
- [35] V. Proust, A. Gossard, J. Schaeperkoetter, S. Vannier, T. David, Y. Barré, S. Misture, A. Grandjean, H.C. zur Loye, Design and characterization of hierarchical aluminosilicate composite materials for Cs entrapment: Adsorption efficiency tied to microstructure. *Journal of Water Process Engineering* **51**, 103381 (2023).
- [36] A. Maleki, Z. Hajizadeh, V. Sharifi, Z. Emdadi, A green, porous and eco-friendly magnetic geopolymer adsorbent for heavy metals removal from aqueous solutions. *Journal of Cleaner Production* **215**, 1233–1245 (2019).
- [37] S.K. Mondal et al., Investigating the microstructure of high-calcium fly ash-based alkali-activated material for aqueous Zn sorption. *Environmental Research* **198**, July 2020, 110484 (2021).
- [38] P. Suresh Kumar, L. Korving, K.J. Keesman, M.C.M. van Loosdrecht, G.J. Witkamp, Effect of pore size distribution and particle size of porous metal oxides on phosphate adsorption capacity and kinetics. *Chemical Engineering Journal* **358**, 160-169 (2019).
- [39] Y. Qiao, L. Xinyu, C. Bai, H. Li, J. Yan, Effects of surfactants / stabilising agents on the microstructure and properties of porous geopolymers by direct foaming. *Journal of Asian Ceramic Societies* **9**, 1, 1-12 (2021).
- [40] Y. Liu, Y. Meng, X. Qiu, F. Zhou, H. Wang, S. Zhou, C. Yan, Novel porous phosphoric acid-based geopolymer foams for adsorption of Pb (II), Cd (II) and Ni (II) mixtures: Behavior and mechanism. *Ceramics International* **49** (4), 7030-7039 (2023).
- [41] A. Hajimohammadi, T. Ngo, P. Mendis, J. Sanjayan, Regulating the chemical foaming reaction to control the porosity of geopolymer foams. *Materials & Design* **120**, 255-265 (2017).
- [42] V. Ducman, L. Korat, Characterisation of geopolymer fly-ash based foams obtained with the addition of Al powder or H₂O₂ as foaming agents. *Materials Characterisation* **113**, 207-213 (2016).
- [43] T.H. Tan, K.H. Mo, S.H. Lai, T.C. Ling, Synthesis of porous geopolymer sphere for Ni (II) removal. *Ceramics International* **47** (20), 29055-29063 (2021).
- [44] K. Liang, X.Q. Wang, C.L. Chow, C. Lau, A review of geopolymer and its adsorption capacity with molecular insights: A promising adsorbent of heavy metal ions. *Journal of Environmental Management* **322**, 116066 (2022).
- [45] J. Tang, P. Liu, S. Xue, Y. Li, Y. Zhao, K. Huang, Z. Liu, Optimization of coal fly ash-based porous geopolymer synthesis and application for zinc removal from water. *Ceramics International* **49** (4), 5828-5833 (2023).
- [46] J. He, J. Q. Gao, X. Song, X. Bu, J. He, Effect of foaming agent on physical and mechanical properties of alkali-activated slag foamed concrete, *Construction and Building Materials* **226**, 280-287 (2019).
- [47] A. Gadkar, A.K.V. Subramaniam, Porosity and pore structure control in cellular geopolymer using rheology and surface tension modifier. *Construction and Building Materials* **323**, 16600 (2022).